

A study on performance of SMA mixes with CRMB-55

¹ Bipin Kumar Singh, ² Vikas Kumar Pandey, ³ Dr. Anil Dixit, ⁴ Dr. Sanj, ⁵ Dr. R Sanjeevi

¹ Research Scholar in Civil Engineering Department in OPJS University Churu, Rajasthan, India

² Assistant Professor in Civil Engineering Department in NIMS University Shobhanagar Jaipur, Rajasthan India

³ Professor in Civil Engineering Department in NIMS University Shobhanagar Jaipur, Rajasthan India

^{4,5} Assistant professor in Nims University shobhanagar Jaipur, Rajasthan, India

Abstract

In the post globalization era, India is witnessing significant growth in every sector which is evident by rapid growth in infrastructure developments. The country is building a huge network of expressways, national highways and rural roads and improvement programs involving large investments. The durability of the road surfaces depends largely on the type and quality of bitumen used and quality control exercised in the production, transportation, mixing, and compaction, to cope up with ever changing rapid growth of laden vehicles with time posing heavy stresses on roads. It is the prime responsibility of researchers, contractors to use such material which modifies the properties of Bitumen and imparts additional strength, elasticity and other beneficial properties to make it better able to withstand high traffic loads, extreme weather conditions and other forms of stresses. Previous studies on CRMB 55 for moderate climatic areas suggest that use of it leads to excellent pavement life, driving comfort and low maintenance.

In this present study, initially paper deals with scientific analyses physical properties for crushed stone aggregate for Dense Bituminous Macadam (As Per MoRTH Table: 500-8). Properties are carefully accessed of CRMB 55 with and without addition in small doses of Chemical Zycosoil to fulfill the basic requirements of standard codes. Different mix design characteristics were determined out using Marshall Method for Dense Bituminous Macadam using CRMB 55 with and without addition in small doses of Chemical Zycosoil.

Keywords: CRMB 55, Dense Bituminous Macadam, Marshall Mix Design, Zycosoil

1. Introduction

The growth rate of vehicles is the backbone of economic development of any country. India is the second fastest growing automobile industry in the world. These have brought excitement amongst business leader over the potential enormous vehicle industry and have drawn attention of likely future course of environmentalists and pavement engineers too. Here lies the utmost important responsibility of highway engineer in world to implement sustainable solutions in the road construction industry which is paramount as one of the major research topics. The road needs to be updated to meet the quality and quantity of performance to sustain repeated vehicle loadings, climatic changes and riding quality. Bitumen modification is needed to sustain the stresses of vehicles with other changes in properties.

CRMB 55 is a special type of bitumen obtained from HINCOL, Savli, Vadodara which is prepared for improving the properties by blending with crumb rubber and special type of additives to make the material resistant to temperature variations, weathering and high traffic loads. CRMB 55 for dense bituminous macadam design is taken into consideration and careful analysis of necessary properties of it, moisture susceptibility and DBM mixes with and without Zycosoil chemical additive in suitable doses is carried out.

Prof. Justo *et al* (2002) ^[8], at the Centre for Transportation Engineering of Bangalore University compare the properties of the modified bitumen with ordinary bitumen. It was observed that the penetration and ductility values of the modified bitumen decreased with the increase in proportion of

the plastic additive, up to 12 percent by weight. Therefore the life of the pavement surfacing using the modified bitumen is also expected to increase substantially in comparison to the use of ordinary bitumen.

Shankar *et al* (2009) ^[10], crumb rubber modified bitumen (CRMB 55) was blended at specified temperatures. Marshall's mix design was carried out by changing the modified bitumen content at constant optimum rubber content and subsequent tests have been performed to determine the different mix design characteristics and for conventional bitumen (60/70) also. This has resulted in much improved characteristics when compared with straight run bitumen and that too at reduced optimum modified binder content (5.67 %).

S.D.Katara, C.S.Modhiya, N.G.Raval (2014) ^[11] stated that fly ash and waste tyre of vehicles is one of the most industrial waste residues in India. Fly ash is the main solid waste discharged by coal-fired power plant. In India, the annual emission of fly ash is more than 0.3 billion tons, and it is one of the main industrial waste residue. The use of four wheeler, two wheeler vehicles etc. is increasing day by day. As a result amount of waste tyres also increasing. Waste tyres in India are categorized as solid or hazardous waste. It is estimated that about 60 per cent of waste tyres are disposed via unknown routes in the urban as well as rural areas. This leads to various environmental problems which include air pollution associated with open burning of tyres and aesthetic pollution.

Therefore, it is necessary to utilize the wastes effectively with technical development in each field. A good design of Modify bituminous mix is expected to result in a mix which is

adequately strong, durable and resistive to fatigue and permanent deformation and at the same time environment friendly and economical. A mix designer tries to achieve these requirements through a number of tests on the mix with varied proportions of material combinations and finalizes the best one. The research result shows that the Marshall method of bituminous mix design was carried out for varying percentages of Fly ash to determine the different mix design characteristics.

2. Materials and Methods

Recognition of physical properties and characteristics assists

the engineers in evaluating the different aggregates to be used in highway construction. In this paper crushed stone aggregate (coarse, fine and filler) obtained from Timba Quarry village Panchamahar, Godhra was used to prepare the dense bituminous macadam mix specimens. The material needs to correspond to best performance parameter fulfilling the ideal conditions of mix as specified in Ministry of Road Transport and Highways specifications in India. Physical Requirements for Coarse Aggregate for Dense Bituminous Macadam is shown in Table 1 and Table 2 represents various properties of Aggregates.

Table 1: Physical Requirements for Coarse Aggregate for Dense Bituminous Macadam

Sr. No.	Property	Test	Specification	Test Result
1	Cleanliness (dust)	Grain size analysis	Max 5 % passing 0.075 IS-Sieve	Pas.37.5-Ret.24mm- 0.48
				Pas.24-Ret.14 mm- 0.78
				Pas. 14 -Ret. 7 mm- 0.88
2	Particle shape	Flakiness & Elongation Indices (Combined)	30% Max	25.65
3	Strength	Aggregate Impact Value(AIV)	27 % Max	11.50
4	Durability	Soundness		
		Magnesium Sulphate	Max 18 %	0.70%
		Sodium sulphate	Max 12 %	0.59%
5	Stripping	Coating and Stripping Bitumen Aggregate Mixtures	Min. Retained Coating 95 %	100.00
6	Atterberg's Limit	Plasticity Index	4 %Max	Non-Plastic

Table 2: Properties of Aggregates

Size of Aggregate	Aggregate Proportions	Bulk Sp.Gravity	Apparent Sp.Gravity	Water Absorption
50 - 28 mm	16%	2.853	2.928	0.90
28 - 22 mm	8%	2.849	2.930	0.97
22 - 14 mm	23%	2.861	2.955	1.11
14 - 8 mm	4%	2.854	2.956	1.21
8 mm down	46%	2.850	2.963	1.33
Filler	3%	2.650	-	-

2.1 Design procedure

Crumb rubber Modified Bitumen (CRMB 55) is obtained from Hincol Industry, Savli, Vadodara district, Gujarat. It is a special type of value added bitumen where the properties of are enhanced by blending with crumb rubber and special additives as per the provisions of IRC: SP: 53-2002 and IS 15462:2004. CRMB 55 is recommended for moderate climate areas. It has the advantage of lower susceptibility, skid resistance, better adhesion with aggregates and binder increasing the life of pavement and enhancing water resistance.

This test procedure is used in designing and evaluating DBM mixes and is extensively used in routine test programmed for the paving jobs. Suitably designed bituminous mix will

withstand heavy traffic loads under adverse climatic conditions and also fulfill the requirement of structural and pavement surface characteristics. Initially the Marshall Test specimens are prepared in accordance to the standard procedure for MS-2, with selected aggregate grading and varying bitumen content are prepared and tested for evaluating Marshall Properties. Figure 2-7 shows Test property curves for hot mix design data by the Marshall method. These graphs are used to determine the Optimum design asphalt content of the mix. The optimum binder content is worked out as 4.17% for DBM Mix Design grading – 1 for which on test property curves the design parameters fitting the design Criteria’s as laid down in MoRTH are determined.

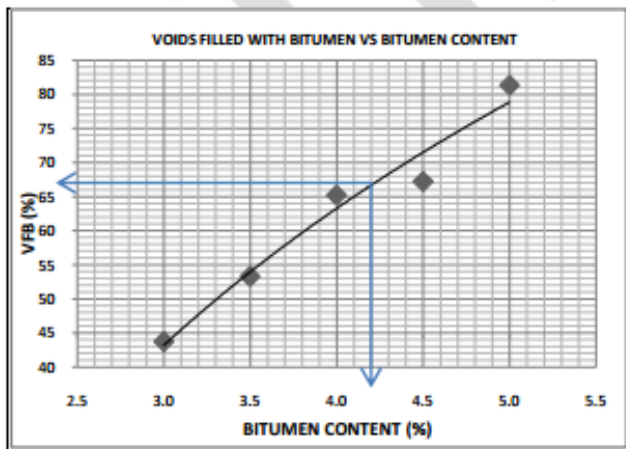


Fig 1: Voids Filled with Bitumen V/s. Bitumen Content

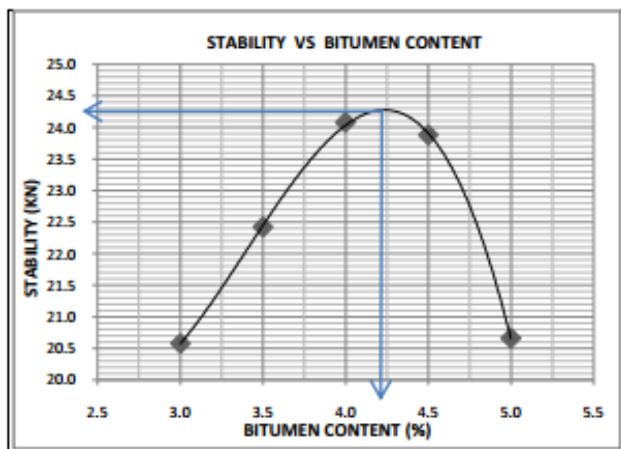


Fig 2: Stability V/s. Bitumen Content

CRMB 55 bituminous mix with 4.17% optimum bitumen content is taken into consideration for following the same procedure of Modified Marshall mix design with and without addition of 0.03%, 0.04% and 0.06% dosage of Zycosoil chemical as an additive at temperature 175°C to compare properties by confirmatory test.

3. Conclusions

The key indicators of the study after careful assessment of critical laboratory studies within the design criteria’s of codal provisions indicates the improvement of performance of DBM crumb rubber modified bituminous mix 55 grade is increased with the addition of Zycosoil nanotechnology chemical as an additive compared to only CRMB 55 mix is as shown:

1. The penetration is a measure of hardness or softness of material. The study reflects that the properties of CRMB 55 changes with the addition of Zycosoil chemical in required doses, as value of penetration decreases material becomes stiff. Also condition of temperature susceptible to increase the workability of bituminous mix is enhanced. With 0.04 % dosage of Zycosoil chemical the change with elastic recovery is also noted indicating more flexibility to the binder and to increase the life of pavement at low temperature.
2. Role of volumetric parameters are utmost important and is associated with careful gradation of aggregates for proper interlocking to increase shear resistance of mix for long

life of pavement. Due care of small compaction under traffic loads can be taken up by adequate voids in without causing bleeding and decrease in stability. Looking to the data after scientific investigation in laboratory regarding the confirmatory test of Marshall mix design using CRMB 55 with 0.04 % Zycosoil chemical reflects the significant rise in stability, unit weight and flow values for better compaction and enhancing the workability conditions.

3. Boiling test showed at 0.04% Zycosoil additive incorporation into DBM mixtures helps to resolve the high level of moisture damage that was noted in the control mix.

4. References

1. Indian Standards. Polymer and Rubber Modified Bitumen- Specification, IS: 15462, 2004.
2. Indian Standards. Methods of test for Aggregates for concrete: Particle size and shape, IS: 2386, Part 1, 1963.
3. Indian Standards. Methods of test for Aggregates for concrete: specific gravity, density, voids, absorption and bulking, IS: 2386, Part 3, 1963.
4. Indian Standards. Methods of test for Aggregates for concrete: Impact value and Abrasion value, IS: 2386, Part 4, 1963.
5. Indian Standards. Method of test for determination of stripping value of road aggregate, IS: 6241, 1974.
6. Indian Standards. Guidelines on the use of Polymer Modified Binder Specifications, IS: SP 53, 2002.
7. Journal of materials in civil engineering. Evaluation of Crumb Rubber Modified Bitumen Mixes.
8. Justo CEG, Veeraragavan A. Utilization of Waste Plastic Bags in Bituminous Mix for Improved Performance of Roads, Centre for Transportation Engineering, Bangalore University, Bangalore, India, 2002.
9. MoRTH. Ministry of Road Transport and Highways, Government of India for Road and Bridge works, Design of Bituminous Concrete, Section 508, Fourth Revision, 2004.
10. Shankar S, Prasad CSRK. Evaluation of Rutting Potential for Crumb Rubber Modified Bitumen in Asphaltic Mixes. Emirates Journal for Engineering Research, 2009; 14(2):91-95.
11. Katara SD, Modhiya CS, Raval NG. Influence of Modify Bituminous Mix with Fly Ash. International Journal of Engineering and Technical Research (IJETR) ISSN: 2321-0869. 2014; 2(4).